

Citation for published version:

Abdeldjouad, L, Asadi, A, Ball, R, Nahazanan, H & Huat, B 2019, 'Application of Alkali-Activated Palm Oil Fuel Ash Reinforced with Glass Fibers in Soil Stabilization', *Soils and Foundations*, vol. 59, no. 5, pp. 1552-1561.
<https://doi.org/10.1016/j.sandf.2019.07.008>

DOI:

[10.1016/j.sandf.2019.07.008](https://doi.org/10.1016/j.sandf.2019.07.008)

Publication date:

2019

Document Version

Peer reviewed version

[Link to publication](#)

Publisher Rights

CC BY-NC-ND

University of Bath

Alternative formats

If you require this document in an alternative format, please contact:
openaccess@bath.ac.uk

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Manuscript Number: SANDF-D-18-00461R1

Title: Application of Alkali-Activated Palm Oil Fuel Ash Reinforced with
Glass Fibers in Soil Stabilization

Article Type: Technical Paper

Keywords: Glass fibers; Alkaline activation; Ground improvement;
Geopolymerisation.

Corresponding Author: Dr. Lokmane Abdeldjouad, Ph.D.

Corresponding Author's Institution: Universiti Putra Malaysia

First Author: Lokmane Abdeldjouad, Ph.D.

Order of Authors: Lokmane Abdeldjouad, Ph.D.; Afshin Asadi, PhD; Richard
Ball, PhD; Haslinda Nahazanan, PhD; Bujang Huat, PhD

Abstract: The feasibility of using palm oil fuel ash (POFA) as a precursor for alkali activation reactions in combination with glass fibers as a discrete reinforcement has been investigated. Experimental work has focused on shear strength (using unconfined compression tests) and the tensile strength (using indirect tensile tests and flexural tests). According to the results, it was found that the peak stress increased and the post-peak behavior was modified from a brittle to a more ductile response depending on the amount of fiber reinforcement in the alkali-activated mixtures. Analysis of the microstructures revealed that the most significant factor contributing to the enhanced behavior of the reinforced mixtures was the interaction between the geo-polymeric matrix and fiber surface. This work brings new insights to the soil stabilization industry providing an effective method of enhancing the properties of soil treated by alkali activation of POFA (a low-value agro-waste by-product) through the inclusion of glass fiber additions. This brings advantages over the traditional calcium-based binders (i.e. lime and cement) as their production involves the emission of carbon dioxide, a contributing factor to the significant global warming.

Application of Alkali-Activated Palm Oil Fuel Ash Reinforced with Glass Fibers in Soil Stabilization

Lokmane Abdeldjouad¹, Afshin Asadi², Ball R. J.³, Haslinda Nahazanan¹,
Bujang B. K. Huat¹

¹Department of Civil Engineering, Faculty of Engineering, Universiti Putra Malaysia, Serdang, Selangor, Malaysia. Email: abdeldjouad.apply@gmail.com

²International College of Auckland, Auckland, New Zealand

³BRE Centre for Innovative Construction Materials, Department of Architecture and Civil Engineering, University of Bath, Bath, UK

Corresponding author: Lokmane Abdeldjouad (e-mail: abdeldjouad.apply@gmail.com), Haslinda Nahazanan (e-mail: n_haslinda@upm.edu.my)

ABSTRACT

The feasibility of using palm oil fuel ash (POFA) as a precursor for alkali activation reactions in combination with glass fibers as a discrete reinforcement has been investigated. Experimental work has focused on shear strength (using unconfined compression tests) and the tensile strength (using indirect tensile tests and flexural tests). According to the results, it was found that the peak stress increased and the post-peak behavior was modified from a brittle to a more ductile response depending on the amount of fiber reinforcement in the alkali-activated mixtures. Analysis of the microstructures revealed that the most significant factor contributing to the enhanced behavior of the reinforced mixtures was the interaction between the geo-polymeric matrix and fiber surface. This work brings new insights

1
2
3
4 24 to the soil stabilization industry providing an effective method of enhancing the
5
6
7 25 properties of soil treated by alkali activation of POFA (a low-value agro-waste by-
8
9 26 product) through the inclusion of glass fiber additions. This brings advantages over
10
11 27 the traditional calcium-based binders (i.e. lime and cement) as their production
12
13
14 28 involves the emission of carbon dioxide, a contributing factor to the significant
15
16 29 global warming.

17
18
19
20 30 *Key words:* **Glass fibers, Alkaline activation, Ground improvement,**
21
22 31 **Geopolymerisation**

23 24 25 32 **INTRODUCTION**

26
27
28 33 Soil stabilization is applied to soils in order to improve their engineering
29
30 34 characteristics through the additions of various different additives (Mohammadinia
31
32 35 et al. 2017; Tabarsa et al. 2018; Kamaruddin et al. 2019). Calcium-based binders
33
34 36 such as cement and lime are widely used binders in soil stabilization (Kazemian et
35
36 37 al., 2009; Pourakbar et al. 2015b; Anggraini et al. 2016; Bahmani et al. 2016).
37
38 38 Although such traditional calcium-based binders can improve several engineering
39
40 39 properties of soils, they have several shortcomings, especially when viewed from an
41
42 40 environmental perspective. For instance, the cement industry is one of the primary
43
44 41 producers of carbon dioxide. Cement generates around 7% of artificial carbon
45
46 42 dioxide emissions due to carbonate decomposition (Gartner, 2004; Matthews et al.,
47
48 43 2009). Therefore the development of new soil binders with lower environmental
49
50 44 impact and equal or better performance compared to traditional alternatives is of
51
52 45 great scientific and global importance.

Alkali-activated binders are known as high-performance inorganic materials. They have developed greatly in recent years on a global scale. Alkali-activated binders are synthesized by reacting amorphous alumino-silicate source materials such as fly ash, palm oil fuel ash, rice husk ash, metakaolin, calcium carbide residue, ground granulated blast furnace slag with an alkali (mostly sodium or potassium) or an alkali earth metal such as calcium (Davidovits 1988, 1991; Yunsheng et al. 2008). This process involves the dissolution of mineral alumino-silicates, followed by hydrolysis and condensation of the aluminum and silicon components (Davidovits 1988, 1991; Yunsheng et al. 2008). The result is a three-dimensional, essentially amorphous, alumino-silicate gel. According to previous studies, to have a positive effect on the mechanical properties of the alkali-activated binders and on the development rate of such properties, it is preferred to use calcium in the mixture to speed the development of calcium alumino-silicate hydrated gel (C.A.S.H.) along with sodium alumino-silicate hydrated gel (N.A.S.H.) (Cristelo et al. 2012a; Winnefeld et al. 2010). Due to the excellent engineering properties, alkali-activated binders have the potential to be considered as the material of choice for highly demanding geotechnical applications (Horpibulsuk et al. 2015; Pourakbar and Huat 2016). One particular application, focused on by some recent research papers is soil stabilization (Cristelo et al. 2011, 2012b, 2013, 2015b; Pourakbar et al. 2015b; Pourakbar et al. 2017; Arulrajah et al. 2016; Liu et al. 2016;; Alsafi et al. 2017; Mohammadinia et al. 2018; Muhammad et al. 2018; Latifi et al. 2018a, 2018b; Elkhebu et al. 2019; Abdeldjouad et al. 2019a, 2019b; Dehghan et al. 2018). The authors of these papers showed that the binding gel (either N.A.S.H. or C.A.S.H.) is

1
2
3
4 69 developed inside the soil voids, helping to form more compact microstructures and,
5
6
7 70 as a result, improved compressive strength.
8

9
10 71 One of the precursors that has been used is POFA because it is widely produced
11
12 72 in large quantities in East Asian and West African countries by the oil palm industry
13
14 73 owing to the burning of empty fruit bunches, fibre, and palm oil shells as fuel to
15
16 74 generate electricity, where the waste, collected as ash, becomes POFA.
17

18
19 75 Despite the fact that alkali-activated binders have shown significant peak
20
21 76 compressive strength in most cases, they also have a tendency to become brittle post-
22
23 77 peak (Pourakbar et al. 2015b). This post-peak limitation is important in some
24
25 78 geotechnical applications (Correia et al. 2015). For example, when seismic loads or
26
27 79 high lateral earth pressures or horizontal displacements are expected (Pourakbar and
30
31 80 Huat 2017; Nissa Mat Said et al. 2018). It is known that when fibers of relatively
32
33 81 high tensile strength are embedded in a soil matrix, shear stresses are generated
34
35 82 between the soil particles, which are then transferred to the fibers in form of tensile
36
37 83 strength such as glass fibre, basalt fibre and polypropylene fibre, which increases the
38
39 84 overall soil strength and rapids a brittle-to-ductile post-peak behaviors transition
40
41 85 (Cristelo et al. 2015a). Due to the highly alkaline environment generated by the
42
43 86 stabilizing agent used in the study, it was necessary to select a compatible fiber type.
44
45 87 Through an extensive review of the literature, glass fibers were identified as
46
47 88 possessing appropriate mechanical properties in terms of tensile, compressive and
48
49 89 flexural strengths (Nematollahi et al. 2014). Glass fibers are composed of a number
50
51 90 of different elements such as potassium and other oxides with the main components
52
53 91 being approximately 60% of SiO_2 , 13% of Al_2O_3 and 22% of CaO . In strong alkaline
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4 92 conditions, these fibers may undergo an alkali-silica reaction where silica and
5
6
7 93 calcium are released. This may weaken the fibers but also provide a stronger
8
9 94 mechanical bond with the surrounding soil matrix.

10
11 95 This paper is focused on the development of an alternative alkaline activated
12
13 96 binder for soil stabilization purposes, based on a previously POFA and potassium-
14
15
16 97 based activators. In addition, the importance of glass fibers incorporated into the
17
18 98 mixture as a source of discrete reinforcement was a focus of this work. The
19
20 99 mechanical response has been evaluated through two tests allowing the
21
22 100 characterization of compressive (uniaxial compression tests) and tensile (indirect
23
24 101 tensile and flexural tests) strengths. Microstructural analysis of the soils before and
25
26 102 after stabilization was investigated using SEM with EDS and FTIR.
27
28
29
30
31

32 103 **EXPERIMENTAL INVESTIGATION**

33 34 104 **Materials**

35
36
37 105 According to the Unified Soil Classification System (ASTM 2010), the soil used
38
39 106 in this study is classified as medium plasticity sandy clay (CL). Table 1 shows the
40
41 107 physical characteristics of the soil.
42
43
44

45 108 The POFA for the alkaline activation reactions was collected from a factory in
46
47 109 Johor Bahru in Malaysia. To obtain a suitable size, shape, and chemical composition,
48
49 110 POFA was initially subjected to a pretreatment including calcination and grinding
50
51 111 (Pourakbar et al. 2015a). After POFA was dried for 24 hours in an oven, at 105°C,
52
53 112 the resulted particles were ground in an 80 cm diameter ball-mill for 24 hours and
54
55 113 then passed through a 300 µm sieve. Next, in order to remove any unburned carbon,
56
57 114 the ground POFA was heated in an electric furnace at 440°C for approximately 1
58
59
60
61
62
63
64
65

1
2
3
4 115 hour. A similar lab scale pretreatment was reported by others (e.g. Pourakbar et al.
5
6 116 2015a) who demonstrated the effectiveness of this method for increasing the specific
7
8 117 surface and reactivity of the ash. There is a need for further research in order to
9
10 118 launch this technology into the construction market. Following the pretreatment, an
11
12 119 elemental analysis was performed using X-ray fluorescence (XRF) spectrometry
13
14
15
16 120 (Table 2).
17
18
19

20 121 Commercially available glass fibers were added at different levels of between 1
21
22 122 and 6% by dry weight to samples of the soil. The fiber's chemical characteristics
23
24 123 were readily available from the manufacturer and reported in Table 2.
25
26
27

28 124 Due to its known efficiency, potassium hydroxide (KOH) was added as a source
29
30 125 of K^+ cations to increase the alkalinity thus performing the role of an activator. As
31
32 126 previously supplied by the company R&M Chemical, the reagent was available in
33
34 127 pellet form which was diluted using sufficient distilled water to achieve a
35
36 128 concentration of 10 molars (Pourakbar et al. 2016b; Abdeldjouad et al. 2019a,
37
38 129 2019b). Since KOH reacts exothermically with water, the solution formed was
39
40 130 allowed to cool to ambient temperature before use.
41
42
43
44

45 131 **Mixing Methodology**

46
47 132 Table 3 presents the composition of each mixture tested. There are three types of
48
49 133 mixtures, based on the stabilization/reinforcement level including un-stabilized soil
50
51 134 (S), activator-soil-binder (KSP), and activator-soil-binder-fiber (KSPG). While
52
53 135 testing of the original, un-stabilized soil was included to provide an adequate
54
55 136 reference regarding the analysis of the KSP and KSPG mixtures.
56
57
58
59
60
61
62
63
64
65

1
2
3
4 137 The dry soil was initially mixed with POFA by hand, and also whenever
5
6 138 required with glass fibers (1 to 6%). Then, the required dosage of air-dried soil and
7
8
9 139 15% of POFA was mixed by adding the cooled alkaline solution with the specified
10
11 140 weights of glass fiber (percent by dry weight of mixture) until a uniform blend was
12
13
14 141 reached.

16 142 **Unconfined Compressive Strength Tests**

18
19 143 The specimens were prepared right after the aforementioned mixing procedure
20
21 144 by manual compaction in a cylindrical mold, 50 mm in diameter and 100 mm high,
22
23 145 using a 45 mm diameter steel rod to apply a static load in three similar layers. A dry
24
25
26 146 density value of 1.58 Mg/m^3 was targeted for all mixtures.

27
28
29 147 Moisture loss was prevented by immediately wrapping the specimens in
30
31 148 polythene plastic covers after extrusion. To obtain a state of approximate saturation
32
33 149 before the UCS tests, the specimens were unwrapped and submerged in water for the
34
35
36 150 last 24 hours prior to the tests. This saturation was applied to all the specimens to
37
38 151 eliminate the positive effects of suction on the specimens' compressive strength,
39
40 152 except for the specimens of un-stabilized soil (S) because of the loss of structural
41
42
43 153 integrity when submerged.

44
45 154 Unconfined compressive strength (UCS) measurement was conducted after a
46
47
48 155 curing period of 7 and 28 days in accordance with Part 7: Clause 7 of BS 1377
49
50 156 (1990). UCS values were measured in three different specimens, and the results were
51
52
53 157 accepted only if they deviated less than 5% from the average. An Instron 3382
54
55 158 universal testing machine, fitted with a 100 kN load cell, was used for these tests,
56
57
58 159 which were carried out under monotonic displacement control at a rate of 0.2
59
60
61
62
63
64
65

1
2
3
4 160 mm/min. The entire stress-strain curve was obtained from each test and after
5
6
7 161 shearing, all specimens were retained for mineralogical analysis.
8

9 162 **Indirect Tensile Strength Tests**

10
11 163 The indirect tensile strength (ITS) was determined using the method described
12
13
14 164 in ASTM D3379 (1975). Cylindrical specimens were used, 100 mm in length and
15
16 165 50 mm in diameter. The tests were performed after a curing period of 28 days,
17
18
19 166 applying a monotonic load speed of 0.6 mm/min on opposite sides of the specimen.
20
21 167 The ITS was calculated based on the peak force applied using Eq. (1)
22

23
24 168
$$ITS = \alpha \frac{2P}{\pi DL} \quad (1)$$

25

26 169 where P = maximum load applied; D = diameter of the sample; L = length of the
27
28
29 170 sample; and α = shape parameter, which can be estimated as $\alpha = 0.2621k + 1$, in
30
31 171 which k= length/diameter ratio of the specimen (Pourakbar et al. 2016a).
32

33 172 **Flexural Strength Tests**

34
35
36 173 Similar specimens to those described for the ITS test was used. Flexural strength
37
38
39 174 was measured after 28 days curing using a three-point bending test according to
40
41 175 ASTM D1635 (2012), under a monotonic speed of 0.1 mm/min. A support span of
42
43
44 176 60 mm was used. The flexural stress for the circular section of the outer layer of the
45
46 177 specimen was calculated as follows:
47

48 178
$$\text{First peak strength } f = \frac{PL}{\pi r^3} \quad (2)$$

49

50
51 179 where P = maximal applied load; r = radius of the specimen; and L = support span.
52

53 180 **Microstructural Analysis**

54
55
56 181 To understand the underlying mechanism of stabilization in this study, selected
57
58
59 182 specimens were analyzed (after submitted to the respective UCS test) using a
60
61
62
63
64
65

1
2
3
4 183 scanning electron microscope (SEM) and Fourier transform infrared spectroscopy
5
6 184 (FTIR). For the SEM/Energy dispersive X-ray spectroscopy (EDS) analysis, the
7
8
9 185 crushed treated soil specimens were attached to Al-stubs with double-sided carbon
10
11 186 tabs and then coated with a thin layer of platinum in a sputter coater. The selected
12
13
14 187 samples were eventually examined using SEM and EDS analyses. To conduct the
15
16 188 FTIR test, the KBr pellet technique was used (3.5 mg of crushed specimens mixed
17
18
19 189 with 800 mg of KBr) for the specified specimens.

20 21 190 **RESULTS**

22 23 191 **Unconfined Compressive Strength**

24
25
26 192 Figs. 1(a-b) show the results from the unconfined compressive strength tests. As
27
28
29 193 it can be seen, alkaline activation treatment induced a brittle behavior and a large
30
31 194 increase in strength after 28 days (KSP mixture). A sudden drop at failure strain of
32
33
34 195 around 2% was observed when compared to the natural soil which was ductile with
35
36 196 an unconfined compressive strength of 0.39 MPa at a failure strain of around 8.5%.
37
38 197 An enhancement was achieved in KSPG group, which was indicated by the gradual
39
40
41 198 drop in strength after a clear peak value was reached, based on the increment of fiber
42
43 199 content and curing time. In this respect, the improvement of stress-strain behavior
44
45
46 200 was more significant when the glass fibers dosage was greater than 2%.

47
48 201 Fig. 2 shows the difference between the compressive strength of the alkaline
49
50
51 202 activation treated soil with and without fibers after curing times of 7 and 28 days.
52
53 203 The inclusion of the fibers increased the compressive strength of the mixtures over
54
55 204 the curing period. For the KSP mixture after 7 and 28 days of curing, values of 0.61
56
57
58 205 and 2.75 MPa were observed, respectively. When the glass fiber content used in
59
60
61
62
63
64
65

1
2
3
4 206 alkaline activation, the compressive strength of the KSPG5 mixture reached values
5
6 207 of 0.97 and 5.7 MPa at 7 and 28 days, respectively. These are 59 and 107% higher
7
8 208 than those obtained with a similar mixture, only without fibers (KSP).
9

10 11 209 **Indirect Tensile Strength** 12 13

14 210 Tensile load-deflection curves of the natural soil and stabilized mixtures, with
15
16 211 and without fiber inclusion and after curing for 28 days, are shown in Fig. 3. It is
17
18 212 noteworthy that the increase in fiber content caused a completely different post-peak
19
20 213 behavior, along with an increase in peak stress and an increase in deflection at peak
21
22 214 stress. For the natural soil, the peak stress value of 0.21 MPa was observed at a
23
24 215 deflection of 0.75 mm. Compared with the potassium-based unreinforced alkaline
25
26 216 activation treated specimens (KSP), an increase in the peak stress value of 0.71 MPa
27
28 217 was observed, with lower deflection, at around 0.35 mm. The ITS of the KSPG3,
29
30 218 KSPG4 and KSPG5 specimens achieved values of 3.59, 3.62 and 6.98 MPa,
31
32 219 respectively with higher deflection, which are increased by 406, 410 and 883%,
33
34 220 relative to the KSP specimen. Improvement in the post-peak behavior of the
35
36 221 reinforced specimens, in which the fibers avoided the immediate structural collapse
37
38 222 of the material by further prolonging the load-bearing capacity of every reinforced
39
40 223 mixture was also noted.
41
42
43
44
45
46
47

48 224 **Flexural Strength** 49

50 225 Flexural load-deflection curves of natural soil and selected stabilized mixtures,
51
52 226 after curing for 28 days and both with (KSPG) and without fiber inclusion (KSP), are
53
54 227 shown in Fig. 4. The natural soil curve exhibited a flexural strength of 0.19 MPa at
55
56 228 approximately 5 mm deflection. In contrast, the curves resulting from the stabilized
57
58
59
60
61
62
63
64
65

1
2
3
4 229 mixtures showed a clear peak which is a direct measure of the flexural strength of
5
6 230 the specimens, as well as a significant increase in the peak flexural load was
7
8
9 231 observed with the addition of the reinforcement, together with an increase in the
10
11 232 corresponding deflection. This effect was especially relevant regarding the 5% fiber
12
13 233 content, i.e., the flexural strength of the KSPG5 mixture reached 1.82 MPa at 1.6
14
15 234 mm deflection, a value 182% higher than that obtained with the similar, unreinforced
16
17
18 235 mixture (KSP) which achieved 0.64 MPa at only 0.55 mm deflection.

21 236 **Microstructural Analysis**

23 237 SEM micrographs of the un-stabilized soil (S), glass fibers, soil-binder mixtures
24
25 238 (KSP) and soil-binder-fibers mixtures (KSPG5), after 28 days of curing, are
26
27 239 presented in Figs. 5(a–d). The more open texture of the untreated soil is shown
28
29 240 clearly in Fig. 5(a), whereas the discrete soil particles are shown more closely bound
30
31 241 in the stabilized material, with the voids seemingly filled (Fig. 5d). This is consistent
32
33 242 with the increase in strength registered by the soil-binder mixtures, relatively to the
34
35 243 original soil (Figs. 1-4).

36 244 The SEM-EDS analysis of the reinforced alkaline activated specimen shown in
37
38 245 Fig. 6 confirms the presence of the elements Si, Al, and Ca which is consistent with
39
40 246 the chemical composition of both the POFA and the fibers. The Si and Al species
41
42 247 dissolved from the POFA (and probably from the colloidal fraction of the soil) were
43
44 248 the main sources of the Si—O—Al and Si—O—Si bonds in the alkaline activated
45
46 249 matrix. But even so, some Si ions may be diffused from the soil surface of the glass
47
48 250 fibers, and hence, contributing to the total aluminosilicate gel and increasing the
49
50 251 density of the Si—O—Si bonds (because of the increase in Si/Al ratio). Also, the

1
2
3
4 252 presence of Si on the surface of the fibers may have promoted the formation of the
5
6 253 network-like bonds observed tightly wrapped around the fibers. This interaction
7
8
9 254 would have restricted the relative movement between the fibers and the soil particles
10
11 255 (Fig. 5e). The results from the SEM-EDS analysis demonstrates that the
12
13
14 256 strengthening mechanism of the alkaline activation can be explained by a well-
15
16 257 formed Si–O–Al and Si–O–Si three-dimensional structure, which agrees well with
17
18 258 the high values recorded in the unconfined compressive strength, indirect tensile
19
20
21 259 strength, and flexural strength tests.
22

23
24 260 The relationship between Al–O, Si–O, Si–O–Si or Si–O–Al asymmetric
25
26 261 stretching peak positions and the extent of the alkaline activation process is complex
27
28 262 but assists towards the study of the mechanism (Ahmari et al. 2012; Buchwald et al.
29
30 263 2007). FTIR was employed to identify the different types of bond within the short-
31
32
33 264 range structure in the two treated mixtures, as shown in Fig. 7, by name KSP and
34
35
36 265 KSPG5. For both KSP and KSPG5, the first peak was observed at wavelengths
37
38 266 between 550 and 750 cm^{-1} , centered at approximately 690.52 cm^{-1} , which may
39
40
41 267 indicate the symmetric extending vibrations of Si–O–Si and Al–O–Si. The second
42
43 268 peak was located at wavelengths between 750 and 850 cm^{-1} , centered at
44
45
46 269 approximately 794.67 cm^{-1} , which may indicate the —CO_3 vibrations in CaCO_3 .
47
48 270 The third and the forth peaks are consistent with the asymmetric extending vibration
49
50
51 271 band of Si–O–T (T = Al, Si), which can be observed in the region between 850 and
52
53 272 1,050 cm^{-1} . Note that this peak represents strong evidence of successful soil
54
55 273 treatment using the alkaline activation process and consequently high values
56
57
58 274 recorded in tests for unconfined compressive strength, indirect tensile strength, and
59
60
61
62
63
64
65

flexural strength. Another main peak within the range 1,400 to 1,430 cm^{-1} was attributed to the extended vibration of the Si-O link which may be an indication of silica polymerization in M-S-H gels. Due to the higher Si/Al ratio in reinforced alkali-activated samples, this peak is much clearer in KSPG5 compared to the peak of the same mixture without fibers (KSP). The broadband in the region 2,300–3,500 cm^{-1} characterizes the spectrum of expansion and deformation vibrations of OH and H-O-H groups from the weakly bound water molecules, which were adsorbed on the surface or trapped in the large cavities between the rings of the activated products.

DISCUSSION

Results indicate that the application of alkaline activation induced a significant increase in strength (Fig. 1). At 28 days, the UCS was higher for treated soil (KSP) compared to that of the original soil. Despite all, there was a tendency towards a more brittle behavior of the binder-soil mixtures registered, which was indicated by the sudden drop in strength after a clear peak value was reached. In order to improve this post-peak tendency, glass fibers were included, that resulted in an elevation in the peak strength of every mixture at every curing period. As shown in Fig. 1, the fibers were effective in reducing the post-peak strength loss. In addition, according to Figs. 1 and 2, it is possible to conclude that the improvement in the strength of the fiber-reinforced mixtures was a function of the curing time and the fiber content. This resulted in a noticeable improvement when the fiber dosage was greater than 3%. Indirect tensile strength and flexural strength tests revealed that the inclusion of

1
2
3
4 297 fiber reinforcement in alkali-activated mixtures increased the peak tensile strength
5
6 298 and improved the post-peak behavior from a brittle to a more ductile response.
7
8

9 299 The microstructural images (Figures 5 and 6) show that the presence of POFA
10
11 300 during the alkaline activation process plays a significant role. Discrete soil particles
12
13 301 in alkali-activated mixtures with POFA show a more closely bounded structure
14
15 302 compared to untreated mixtures, where the seemingly filled voids result in the total
16
17 303 strength increase shown in Fig. 1. Figure 5d shows an SEM micrograph of the POFA
18
19 304 treated soil which indicates that the ultrafine particle size of the POFA led to an
20
21 305 increasingly dense soil matrix. The gaps within the soil particles are filled with
22
23 306 alkali-activated POFA. Moreover, the inclusion of glass fibers in alkaline solutes
24
25 307 were highly effective reinforcing materials. The needle-like structure of the fibers
26
27 308 acted in a similar manner to plant roots by distributing the stresses over a wider area
28
29 309 and inhibiting cleavage propagation (Figure 5 and 6). This resulted in a total
30
31 310 strength increase, as shown previously in Figs. 1-4. This is inconsistent with the
32
33 311 study performed by Nematollahi et al. (2014), who concluded that the fracture
34
35 312 strength of the glass fibers was of great effect when added to a geopolymer matrix.
36
37

38 313 The improved mechanical performance observed in unconfined compressive
39
40 314 strength, indirect tensile strength, and flexural strength tests is related to the alkaline
41
42 315 activation process and presence of glass fibre. The tensile strength and flexural
43
44 316 strength basically increased with the presence of glass fibre. The improved
45
46 317 performance was also largely related to the high calcium content of the fibers, which
47
48 318 may dissolve and subsequently become incorporated into the alkaline activated
49
50 319 matrix (Fig. 6). The additional nucleation sites, provided by the calcium ions, for
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

precipitation of dissolved species (Yip et al. 2008) could contribute to the formation of C-A-S-H gel, in addition to the K-A-S-H gel formed from the activation of the main precursor (POFA). There were two mechanisms identifying the formation of the C-A-S-H gel (Yip et al. 2005). In the first case, both the A-S-H and C-S-H gels act as independent phases. This appears dominant in spectra 2 and 4 obtained from the fibers where the high Ca/Si ratio was observed which indicates partial activation of the fiber's surface and the presence of C-A-S-H gel within the matrix. The second mechanism indicates that the Ca ions act as a charge-balancing agent and are integrated into the C-A-S-H network. However, the second mechanism seems to have dominated in the areas with a low fiber presence, due to the low Ca/Si ratios at other points (Fig 6). The fibers' surface partial dissolution has mostly included Si ions which helped in formation of the microstructural network, hence sticking the fibers surface to the geo-polymeric matrix and improving the mechanical interlocking effect between the fibers and the matrix. This was a very interesting side-effect because the mechanical performance of a soil improved by fiber inclusion, as well-known, depends usually on the characteristics of the fibers, along with the adhesion of the soil-fiber interface (Cristelo et al. 2015a; Tan et al. 2019; Kamaruddin et al. 2019). With the previous considerations in mind, it can be concluded that the simultaneous formation of K-A-S-H gel (from the POFA and the solid surface of the fibers) and C-A-S-H gel (mainly from the calcium present on the solid surface of the fibers) was the main reason for bridging the particles forming the soil matrix and also for improving the internal stability and interfacial interactions between the fibers and the soil.

343 CONCLUSIONS

344 Based on the laboratory tests and analyses presented in this paper, the following
345 conclusions were reached;

- 346 • The compressive strength of the medium plasticity sandy clay was improved
347 with a brittle behavior when POFA as a source binder and potassium
348 hydroxide as an activator were used in the alkaline activation process.
- 349 • The peak tensile strength of the soil was improved when 3 to 5% of glass
350 fibers were included into the alkali-activated treated soil with POFA.
- 351 • Inclusion of glass fibres into the alkali-activated treated soil with POFA
352 improved the post-peak behavior of the soil matrix from a brittle to a more
353 ductile response.
- 354 • From the microstructural analysis, it was concluded that the interaction
355 between the glass fiber surface and the alkali-activated matrix, contributed to
356 the enhanced behavior of the reinforced soil.

358 ACKNOWLEDGMENTS

359 The authors would like to express their gratitude to Universiti Putra Malaysia and
360 Ministry of Science Technology Innovation (MOSTI) for providing financial support
361 during the research under project no: 06-01-04-SF2387.

362 REFERENCES

- 363 Abdeldjouad L., Asadi A., Huat B.K., Jaafar S., Dheyab W., Elkhebu A. (2019a).
364 Effect of Curing Temperature on the Development of Hard Structure of Alkali-
365 Activated Soil. International Journal of GEOMATE, 17 (60), 117-123.

- 366 Abdeldjouad L., Asadi A., Nahazanan H., Huat B.K., Dheyab W., Elkhebu A.
367 (2019b). Effect of Clay Content on Soil Stabilization with Alkaline Activation.
368 International Journal of Geosynthetics and Ground Engineering, 5,
369 doi.org/10.1007/s40891-019-0157-y.
- 370 Ahmari, S., Ren, X., Toufigh, V., & Zhang, L. (2012). Production of geopolymeric
371 binder from blended waste concrete powder and fly ash. Construction and Building
372 Materials, 35, 718–729.
- 373 Alsafi, S., Farzadnia, N., Asadi, A., & Huat, B. B. K. (2017). Collapsibility potential
374 of gypseous soil stabilized with fly ash geopolymer; characterization and assessment.
375 Construction and Building Materials, 137, 390–409.
- 376 Anggraini, V., Asadi, A., Farzadnia, N., Jahangirian, H., & Huat, B. B. K. (2016).
377 Effects of coir fibres modified with Ca(OH)_2 and Mg(OH)_2 nanoparticles on
378 mechanical properties of lime-treated marine clay. Geosynthetics International,
379 23(3), 206-218.
- 380 Arulrajah A., Mohammadinia A., Horpibulsuk S., Samingthong W. (2016). Influence
381 of class F fly ash and curing temperature on strength development of fly ash-
382 recycled concrete aggregate blends. Constr. Build. Mater., 127, 743–750.
- 383 ASTM. (1975). “Tensile strength and Young’s modulus for high-modulus single-
384 filament materials.” ASTM D3379, West Conshohocken, PA.
- 385 ASTM. (2010). “Standard practice for classification of soils for engineering purposes
386 (unified soil classification system).” ASTM D2487, West Conshohocken, PA.

- 1
2
3
4 387 ASTM. (2012). "Standard test method for flexural strength of soil cement using
5
6 388 simple beam with three point loading." ASTM D1635, West Conshohocken, PA.
7
8
9 389 Bahmani, S. H., Farzadnia, N., Asadi, A., & Huat, B. B. K. (2016). The effect of size
10
11 390 and replacement content of nanosilica on strength development of cement treated
12
13 391 residual soil. *Construction and Building Materials*, 118, 294-306.
14
15
16
17 392 British Standards Institution. (1990). "Methods of test for soils and civil engineering
18
19 393 purposes." BS1377, London.
20
21
22 394 Buchwald, A., Hilbig, H., & Kaps, C. (2007) Alkali-activated metakaolin-slag
23
24 395 blends – performance and structure in dependence of their composition. *Journal of*
25
26 396 *Materials Science*, 42(9), 3024–3032.
27
28
29 397 Correia, N. A., Oliveira, P. J. V., and Custódio, D. G. (2015). "Effect of
30
31 398 polypropylene fibres on the compressive and tensile strength of a soft soil,
32
33 399 artificially stabilised with binders." *Geotext. Geomembr.*, 43(2), 97–106.
34
35
36
37 400 Cristelo, N., Cunha, V. M., Dias, M., Gomes, A. T., Miranda, T., and Araújo, N.
38
39 401 (2015a). "Influence of discrete fibre reinforcement on the uniaxial compression
40
41 402 response and seismic wave velocity of a cementstabilised sandy-clay." *Geotext.*
42
43 403 *Geomembr.*, 43(1), 1–13.
44
45
46
47 404 Cristelo, N., Glendinning, S., Fernandes, L., and Pinto, A. T. (2012a). "Effect of
48
49 405 calcium content on soil stabilisation with alkaline activation." *Constr. Build. Mater.*,
50
51 406 29, 167–174.
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 407 Cristelo, N., Glendinning, S., Fernandes, L., and Pinto, A. T. (2013). "Effects of
408 alkaline-activated fly ash and Portland cement on soft soil stabilisation." *Acta*
409 *Geotech.*, 8(4), 395–405.
- 410 Cristelo, N., Glendinning, S., Miranda, T., Oliveira, D., and Silva, R. (2012b). "Soil
411 stabilisation using alkaline activation of fly ash for self compacting rammed earth
412 construction." *Constr. Build. Mater.*, 36, 727–735.
- 413 Cristelo, N., Glendinning, S., and Pinto, A. T. (2011). "Deep soft soil improvement
414 by alkaline activation." *Proc. ICE-Ground Improv.*, 164(2), 73–82.
- 415 Cristelo, N., Miranda, T., Oliveira, D. V., Rosa, I., Soares, E., Coelho, P., and
416 Fernandes, L. (2015b). "Assessing the production of jet mix columns using alkali
417 activated waste based on mechanical and financial performance and CO₂ (eq)
418 emissions." *J. Clean. Prod.*, 102, 447–460.
- 419 Davidovits, J. (1988). "Geopolymer chemistry and properties." *Proc.*, 1st European
420 Conf. on Soft Mineralurgy (Geopolymere '88), J. Davidovits and E. J. Orlinsl, eds.,
421 The Geopolymer Institute, Compiegne, France, 25–48.
- 422 Davidovits, J. (1991). "Geopolymers." *J. Therm. Anal. Calorim.*, 37(8), 1633–1656.
- 423 Dehghan, H., Tabarsa, A., Latifi, N., & Bagheri, Y. (2018). Use of xanthan and guar
424 gums in soil strengthening. *Clean Technologies and Environmental Policy*, 21(1),
425 155–165.
- 426 Elkhebu A., Zainorabidin A., Bakar I., Huat B.K., Abdeldjouad L., Dheyab W.
427 (2019). Alkaline activation of clayey soil using potassium hydroxide & fly ash. *Int.*
428 *J. Integr. Eng.*, 10(9), 99–104.

429 Gartner, E. (2004). Industrially interesting approaches to ‘low-CO₂’ cements.
 430 Cement and Concrete Research, 34(9), 1489–1498.
 431 Horpibulsuk, S., Suksiripattanapong, C., Samingthong, W., Rachan, R., and
 432 Arulrajah, A. (2015). “Durability against wetting–drying cycles of water treatment
 433 sludge–fly ash geopolymer and water treatment sludge–cement and silty clay–
 434 cement systems.” J. Mater. Civil Eng., 10.1061/(ASCE)MT.1943-5533.0001351,
 435 04015078.
 436 Kamaruddin F.A., Huat B.K., Nahazanan H., Anggraini V. (2019). Modified Natural
 437 Fiber on Soil Stabilization with Lime and Alkaline Activation Treated Marine Clay.
 438 International Journal of GEOMATE, 16 (58), 69-75.
 439 Kazemian, S., Asadi, A., Huat, B. B. K. & Prasad, A. (2009). Settlement Problems in
 440 Peat Due to Their High Compressibility and Possible Solution Using Cement
 441 Columns. Fifth Forensic Engineering Congress, doi.org/10.1061/41082(362)26.
 442 Latifi, N., Vahedifard, F., Ghazanfari, E., & Rashid, A. S. A. (2018a). Sustainable
 443 Usage of Calcium Carbide Residue for Stabilization of Clays. Journal of Materials in
 444 Civil Engineering, 30(6).
 445 Latifi, N., Vahedifard, F., Siddiqua, S., & Horpibulsuk, S. (2018b). Solidification-
 446 Stabilization of Heavy Metal-Contaminated Clays Using Gypsum: Multiscale
 447 Assessment. International Journal of Geomechanics, 18(11), 04018150.
 448 Liu, Z., Cai, C., Liu, F., and Fan, F. (2016). “Feasibility study of loess stabilization
 449 with fly ash-based geopolymer.” J. Mater. Civ. Eng., 10.1061/ (ASCE)MT.1943-
 450 5533.0001490, 04016003.

- 1
- 2
- 3
- 4 451 Matthews, H. D., Gillett, N. P., Stott, P. A., & Zickfeld, K. (2009). The
- 5
- 6 452 proportionality of global warming to cumulative carbon emissions. *Nature*,
- 7
- 8 453 459(7248), 829–832.
- 9
- 10
- 11 454 Mohammadinia A., Arulrajah A., Haghighi H., Horpibulsuk S. (2017). Effect of lime
- 12
- 13 455 stabilization on the mechanical and micro-scale properties of recycled demolition
- 14
- 15 456 materials. *Sustainable Cities Soc.*, 30, 58–65.
- 16
- 17
- 18 457 Mohammadinia A., Arulrajah A., D’Amico A., Horpibulsuk S. (2018). Alkali-
- 19
- 20 458 activation of fly ash and cement kiln dust mixtures for stabilization of demolition
- 21
- 22 459 aggregates. *Constr. Build. Mater.*, 186, 71–78.
- 23
- 24
- 25 460 Muhammad, N., Siddiqua, S., & Latifi, N. (2018). Solidification of subgrade
- 26
- 27 461 materials using magnesium alkalization: A sustainable additive for construction.
- 28
- 29 462 *Journal of Materials in Civil Engineering*, 30(10), 04018260.
- 30
- 31
- 32 463 Nematollahi, B., Sanjayan, J., Chai, J. X. H., Lu, T. M. (2014). Properties of fresh
- 33
- 34 464 and hardened glass fiber reinforced fly ash based geopolymer concrete. *Key*
- 35
- 36 465 *Engineering Materials 2014; Vols. 594-595: 629-633.*
- 37
- 38
- 39 466 Nissa Mat Said, K., Safuan A Rashid, A., Osouli, A., Latifi, N., Zurairahetty Mohd
- 40
- 41 467 Yunus, N., & Adekunle Ganiyu, A. (2018). Settlement Evaluation of Soft Soil
- 42
- 43 468 Improved by Floating Soil Cement Column. *International Journal of Geomechanics*,
- 44
- 45 469 19(1), 04018183.
- 46
- 47
- 48 470 Pourakbar, S., Asadi, A., Huat, B. B., and Fasihnikoutalab, M. H. (2015a).
- 49
- 50 471 Stabilization of Clayey Soil Using Ultrafine Palm Oil Fuel Ash (POFA) and Cement.
- 51
- 52 472 *Transp. Geotech.*, 3, 24–35.
- 53
- 54
- 55
- 56
- 57
- 58
- 59
- 60
- 61
- 62
- 63
- 64
- 65

473 Pourakbar, S. and Huat, B. K. (2016). A Review of Alternatives Traditional
 474 Cementitious Binders for Engineering Improvement of Soils. *Int. J. Geotech. Eng.*,
 475 11(2), 206–216.

476 Pourakbar, S., Asadi, A., Huat, B. B., and Fasihnikoutalab, M. H. (2015b). Soil
 477 Stabilization With Alkali-Activated Agro-Waste. *Environ. Geotech.*, 2(6), 359–370.

478 Pourakbar, S., Asadi, A., Huat, B. B., Cristelo, N., and Fasihnikoutalab, M. H.
 479 (2016a). Application of Alkali-Activated Agro-Waste Reinforced With Wollastonite
 480 Fibers in Soil Stabilization. *J. Mater. Civ. Eng.*, 04016206.

481 Pourakbar, S., Huat, B. B., Asadi, A., and Fasihnikoutalab, M. H. (2016b). Model
 482 Study of Alkali-Activated Waste Binder for Soil Stabilization. *International Journal*
 483 *of Geosynthetics and Ground Engineering*, 2, doi.org/10.1007/s40891-016-0075-1.

484 Pourakbar, S., and Huat, B. K. (2017). Laboratory-scale model of reinforced alkali-
 485 activated agro-waste for clayey soil stabilization. *Advances in Civil Engineering*
 486 *Materials*, 6 (1), 83–105.

487 Tabarsa, A., Latifi, N., Meehan, C. L., & Manahiloh, K. N. (2018). Laboratory
 488 investigation and field evaluation of loess improvement using nanoclay-A
 489 sustainable material for construction. *Construction and Building Materials*, 158, 454-
 490 463.

491 Tan T., Huat B.K., Anggraini V., Shukla S.K. (2019). Improving the engineering
 492 behaviour of residual soil with fly ash and treated natural fibres in alkaline condition.
 493 *International Journal of Geotechnical Engineering*,
 494 doi.org/10.1080/19386362.2018.1564854.

- 1
2
3
4 495 Winnefeld, F., Leemann, A., Lucuk, M., Svoboda, P., and Neuroth, M. (2010).
5
6 496 “Assessment of phase formation in alkali activated low and high calcium fly ashes in
7
8 497 building materials.” *Constr. Build. Mater.*, 24(6), 1086–1093.
9
10
11 498 Yip, C. K., Lukey, G., and Van Deventer, J. (2005). “The coexistence of
12
13 499 geopolymeric gel and calcium silicate hydrate at the early stage of alkaline
14
15 500 activation.” *Cem. Concr. Res.*, 35(9), 1688–1697.
16
17
18 501 Yip, C. K., Lukey, G. C., Provis, J. L., and van Deventer, J. S. (2008). “Effect of
19
20 502 calcium silicate sources on geopolymerisation.” *Cem. Concr. Res.*, 38(4), 554–564.
21
22
23 503 Yunsheng, Z., Wei, S., Zongjin, L., Xiangming, Z., and Chungkong, C. (2008).
24
25 504 “Impact properties of geopolymer based extrudates incorporated with fly ash and
26
27
28
29 505 PVA short fiber.” *Constr. Build. Mater.*, 22(3), 370–383.
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

List of Tables

Table 1. Physical characteristics of soil


Basic soil property	Standard	Value
Specific gravity (G _s)	BS 1377-2	2.52
Liquid limit (LL) (%)	BS 1377-2	48.7
Plasticity index (PI) (%)	BS 1377-2	34.5
OMC (%)	BS 1377-4	24
MDD (Mg/m ³)	BS 1377-4	1.58
UCS (kPa)	BS 1377-7	380-390

Table 2. Chemical analysis of soil, POFA and glass fiber analyzed by X-Ray Fluorescence (XRF)


Constituent	Natural soil (%)	POFA (%)	Glass fibers (%)
Silica (SiO ₂)	41.26	46.04	59.9
Alumina (Al ₂ O ₃)	36.96	19.39	13.09
Iron oxide (Fe ₂ O ₃)	10.07	6.10	-
Calcium oxide (CaO)	-	13.87	22.5
Potash (K ₂ O)	11.71	8.61	2.77
Magnesia (MgO)	-	-	2.5
Loss on ignition (LOI)	-	9.68	-

Table 3. Mixture Proportions of Various Series of Test Specimens

Group series	Test number	Samples	UCS test, curing (days)	Flexural strength test, indirect tensile strength test, curing (days)
S	S	Natural soil	-	-
KSP	KSP	10MKOH + Soil + 15% POFA	7, 28	28
KSPG group	KSPG1	10MKOH + Soil + 15% POFA + 1% glass fibers	7, 28	28
	KSPG2	10MKOH + Soil + 15% POFA + 2% glass fibers	7, 28	28
	KSPG3	10MKOH + Soil + 15% POFA + 3% glass fibers	7, 28	28
	KSPG4	10MKOH + Soil + 15% POFA + 4% glass fibers	7, 28	28
	KSPG5	10MKOH + Soil + 15% POFA + 5% glass fibers	7, 28	28
	KSPG6	10MKOH + Soil + 15% POFA + 6% glass fibers	7, 28	28

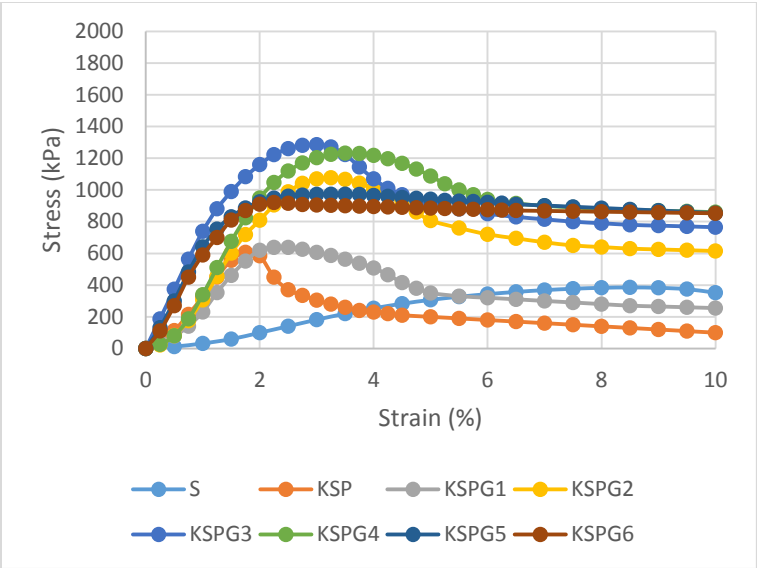

(a)

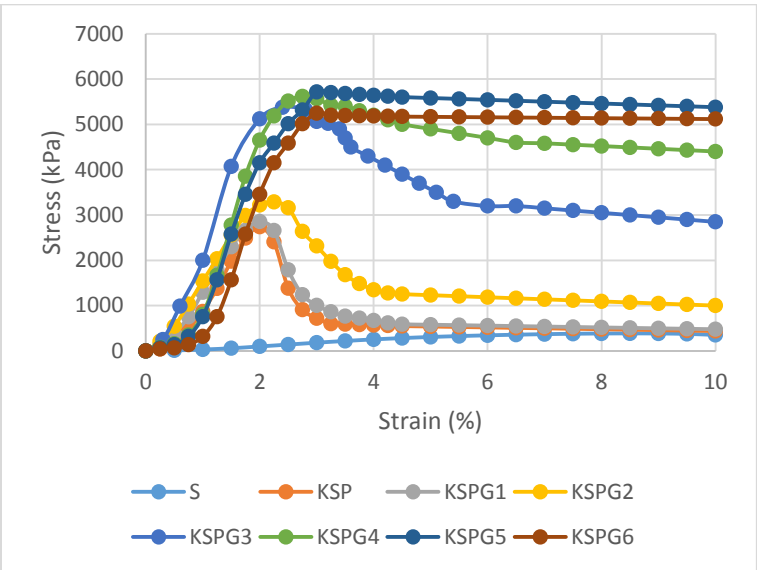

(b)

Fig. 1. Stress-strain behavior of treated soil samples after (a) 7 days and (b) 28 days curing

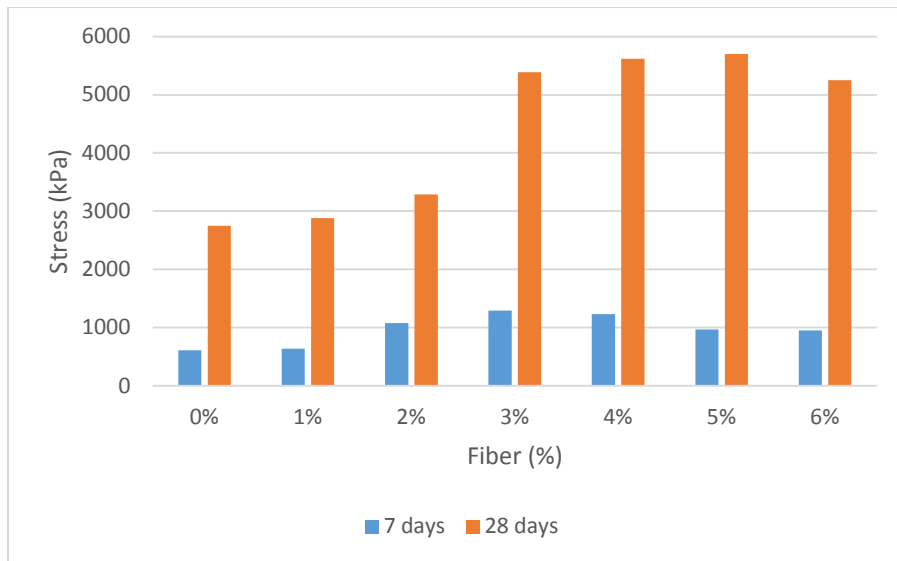


Fig. 2. Compressive strength of treated soil samples after (a) 7 days and (b) 28 days curing

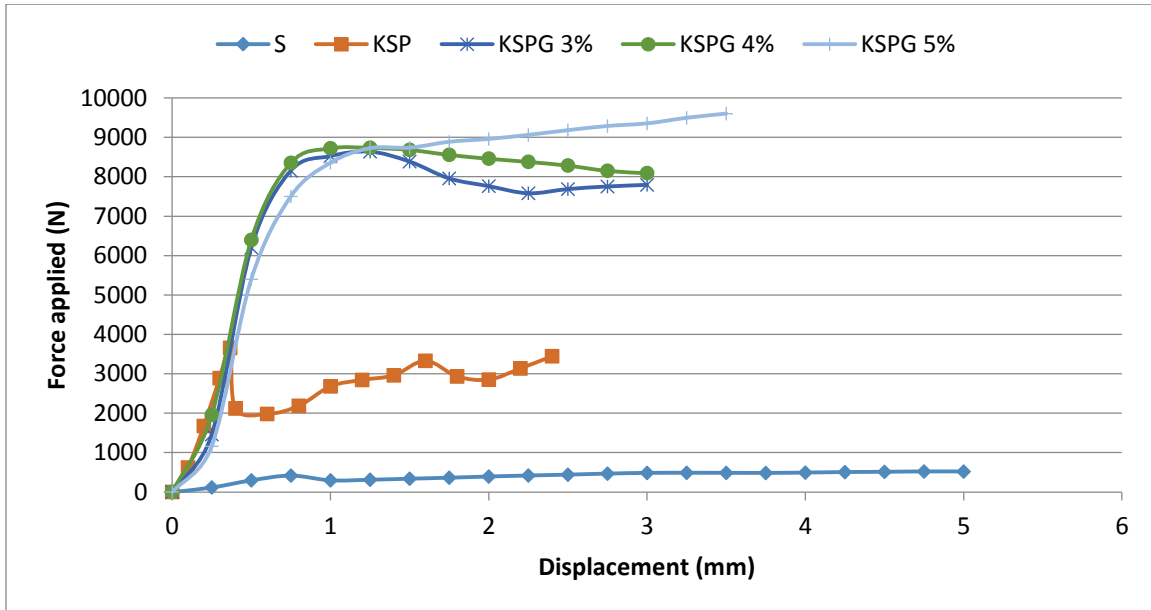


Fig. 3. Tensile load-deflection curves obtained after 28 days of curing



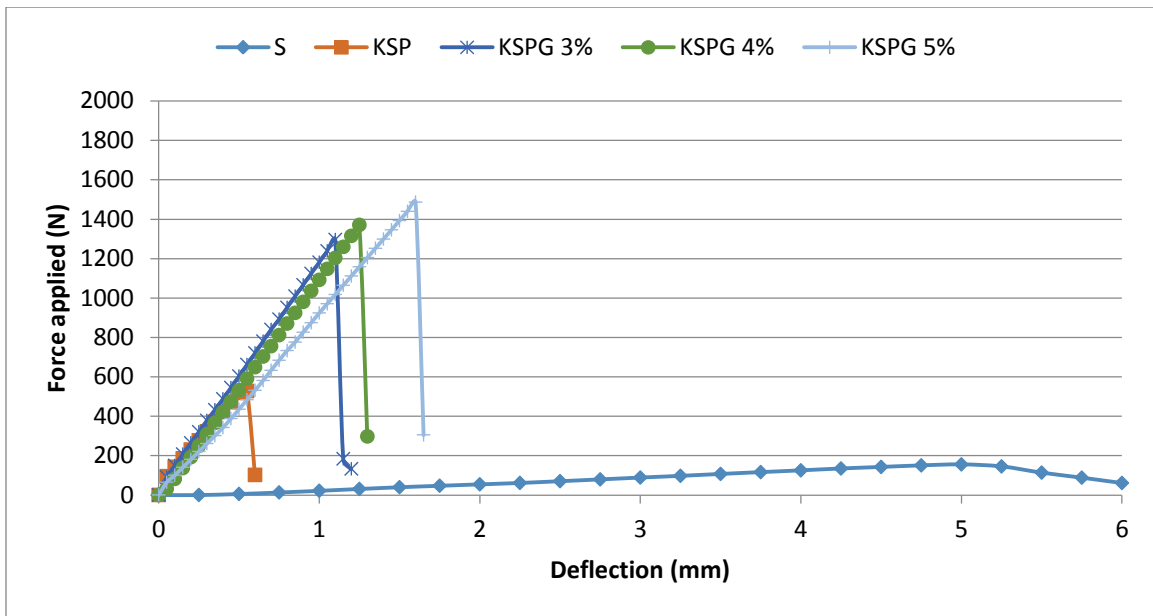


Fig. 4. Flexural load-deflection curves of treated test samples after 28 days of curing.

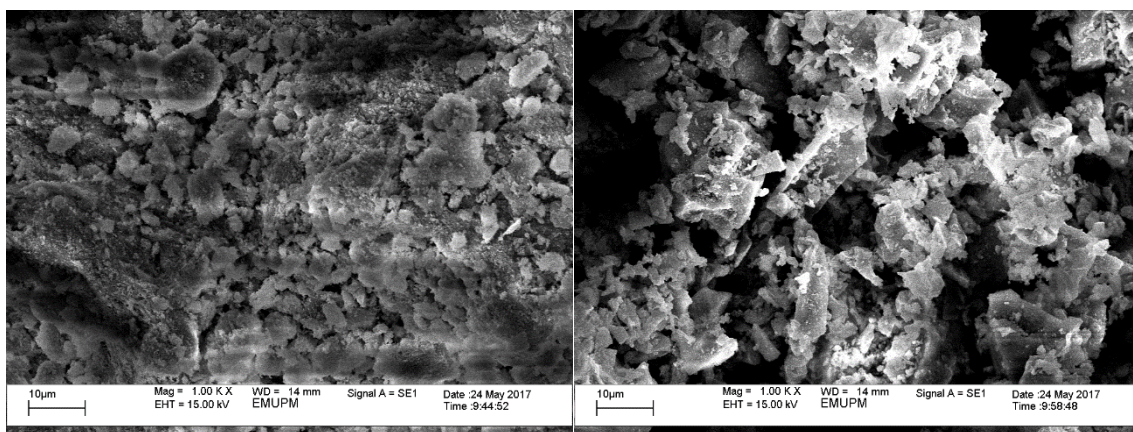


(a)

(b)

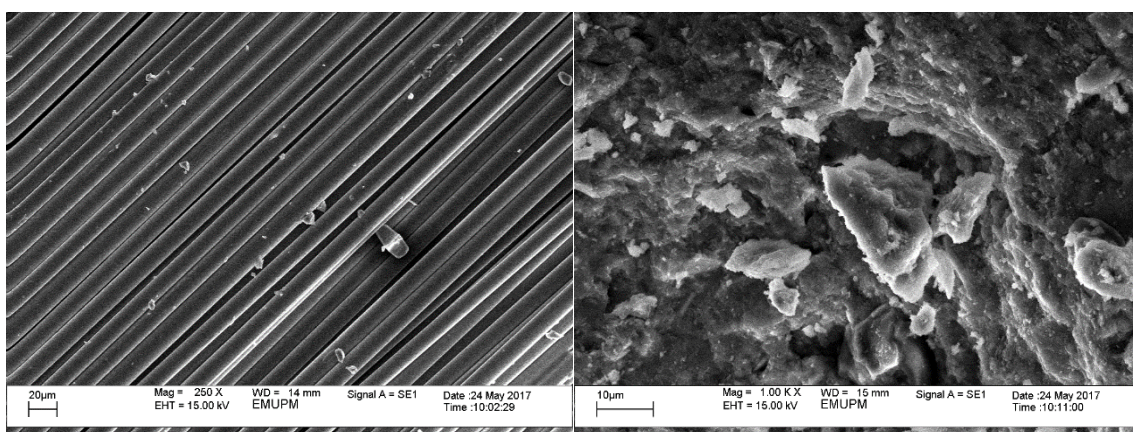

(c)

(d)

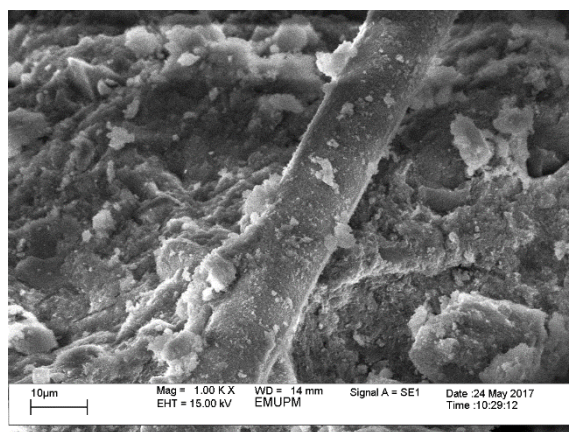

(e)

Fig. 5. SEM micrographs of (a) natural soil (S); (b) POFA; (c) glass fibers; (d) KOH-soil-POFA (KSP); (e) KOH-soil-POFA-fibers (KSPG5).

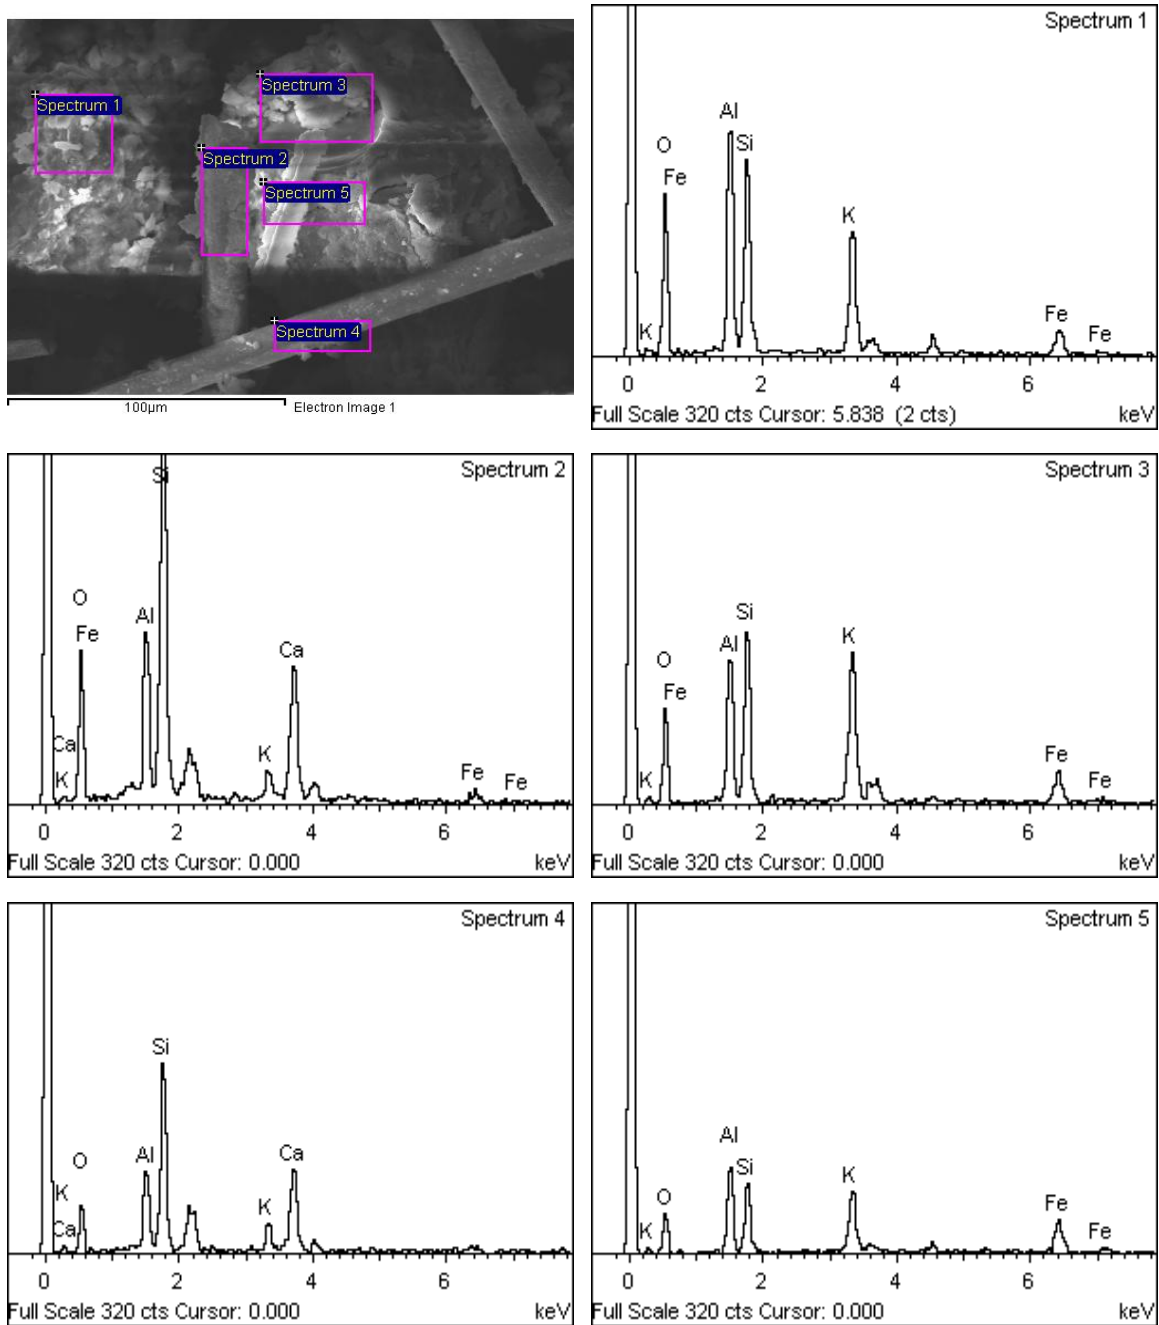


Fig. 6. Micrograph and EDS data of glass fibers inclusion in stabilized soil mixture.

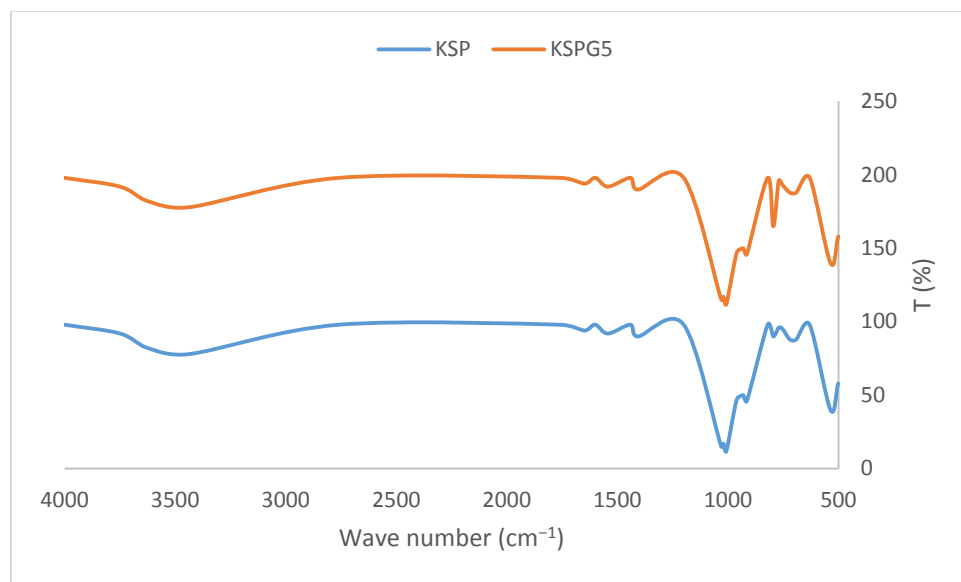


Fig. 7. FTIR of selected test samples.

1. GENERAL COMMENTS TO AUTHORS

The manuscript discusses the feasibility of using palm oil fuel ash (POFA) as a precursor for alkali activation reactions in combination with glass fibers as a discrete reinforcement. Overall, the topic of the article is interesting. It will benefit readers in the field of soil stabilization techniques. This manuscript has been reviewed by experts in this field of study. The reviewers have recommended that the manuscript should be reassessed after extensive revisions. Some of the issues with the current version of the manuscript include grammatical errors throughout, English needs to be checked, literature review needs to be updated, quality of the images needs to be improved, technical items need to be addressed, results and analysis requires additional discussions.

Response: Thank you very much for your constructive comments. The manuscript was proofread by a native speaker, and all comments were responded to. We included several references, and we updated the literature review accordingly. Also, results were further discussed. We highlighted all changes.

2. REVISIONS

- Technical items for which revisions are compulsory:

M1. Abstract: Novelty and significance of this study should be carefully addressed. What are the advantages of the used additive focused in this study relative to traditional additives (i.e., lime, cement and fly ash)? It is suggested that "Abstract" should be rewritten to highlight the key points of this study. It is too poor in its current form.

Response: The abstract was improved. Additionally the introduction was also improved to address the traditional soil binders and environmental issues associated with them and the need for development of new soil binders.

M2. Introduction: The literature covered was mainly from the stabilization in concrete application and since the nature of the stabilization in ground improvement is different from that of concrete applications, it is suggested to review the publication in the field of geotechnincs. Some of the suggested publications are: "Influence of class F fly ash and curing temperature on strength development of fly ash-recycled concrete aggregate blends" and "Alkali-activation of fly ash and cement kiln dust mixtures for stabilization of demolition aggregates" and "Effect of lime stabilization on the mechanical and micro-scale properties of recycled demolition materials".

Response: Thank you for your constructive comments and the suggestions. In addition to the following references, several references were added to address the geotechnical field.

M3. Introduction: This section can enhance with some more recent research on stabilization marginal soil with green additive in the concept of sustainable way:

- a) Nissa Mat Said, K., Safuan A Rashid, A., Osouli, A., Latifi, N., Zurairahetty Mohd Yunus, N., & Adekunle Ganiyu, A. (2018). Settlement Evaluation of Soft Soil Improved by Floating Soil Cement Column. *International Journal of Geomechanics*, 19(1), 04018183.
- b) Latifi, N., Vahedifard, F., Siddiqua, S., & Horpibulsuk, S. (2018). Solidification-Stabilization of Heavy Metal-Contaminated Clays Using Gypsum: Multiscale Assessment. *International Journal of Geomechanics*, 18(11), 04018150.
- c) Muhammad, N., Siddiqua, S., & Latifi, N. (2018). Solidification of subgrade materials using magnesium alkanization: A sustainable additive for construction. *Journal of Materials in Civil Engineering*, 30(10), 04018260.
- d) Latifi, N., Vahedifard, F., Ghazanfari, E., & Rashid, A. S. A. (2018). Sustainable Usage of Calcium Carbide Residue for Stabilization of Clays. *Journal of Materials in Civil Engineering*, 30(6).

- e) Tabarsa, A., Latifi, N., Meehan, C. L., & Manahiloh, K. N. (2018). Laboratory investigation and field evaluation of loess improvement using nanoclay-A sustainable material for construction. *Construction and Building Materials*, 158, 454-463.
- f) Dehghan, H., Tabarsa, A., Latifi, N., & Bagheri, Y. (2018). Use of xanthan and guar gums in soil strengthening. *Clean Technologies and Environmental Policy*, 1-11.

Response: Thank you for your constructive comments and the suggestions. Several references were added to address the geotechnical field.

M4. line 96: is CL the correct terminology? Also, check the state the testing procedure for determination of soil classification.

Response: Yes, It was checked. The classification is correct.

M5. line 111: Considering all the treatment for the preparation of POFA, discuss the feasibility for large scale application.

Response: This study aimed at a lab scale investigation. A discussion has been added to address the need for further research in order to launch this technology into the construction market.

M6. line 124: Why 10 molar?

Response: the references were added.

M7. It would be better to add the FTIR result of pure soil, and soil treated with selected additive to the paper, so the FTIR discussion could be meaningful at that way. Generally, the quality of the figures is not good and those are presented too bleary. More discussion on the UCS test results is necessary, why the strength increased and what mechanism happened between the soil and additive? The latter is necessary to be added for the direct shear test results. The authors should provide a discussion and make a relation between strength tests and micro-structural results (Optical images). Needed more technical discussion and explanation on results.

Response: I appreciate your concern, however, the FTIR was employed to identify the significant role of the 'amorphous' bonds in the alkaline activated matrix as it was discussed, and that is why soil is not included. It should be noted that the SEM, EDS, and FTIR comprehensively supported the mechanism. The discussion on UCS, indirect tensile strength, and flexural tests were improved to address the relationship between strength tests and microstructural tests. The quality of the figures has been improved.

M8. Conclusion is generic; they need to clearly explain their findings in the conclusion not just providing the summary as it currently reads. Authors also need to edit the whole paper to avoid any typos.

The conclusion was improved, and the whole paper has been proofread.